

检测报告

TEST REPORT

报告编号/No.: STS2109106

样品名称

冷轧钢板

Sample Name

/

委托单位

江西华鑫环宇科技集团有限公司

Client

/

检验类别

委托检验

Test Type

Entrustment Inspection

江苏科泰检测技术服务有限公司
Jiangsu Science Test Technology Service Co., Ltd



本报告只对来样负责，并在客户提供信息范围内。本报告在没有完整的签名、盖章情况下不允许复制。任何对结果的怀疑都应在15天内通知，除非另有说明，样品只保留30天。This report is responsible for the receiving samples only and within the limits of information from client. This testing report cannot be reproduced without stamp/signature of tester/checker/signatory, except in full. Any suspicion of results shown hereon should be informed within 15 days. Unless otherwise stated, sample(s) are retained for 30 days only.
Jiangsu Science Test Technology Service Co., Ltd. +86(0)512-36831080
ADD: No. 16 Jinshajiang South Road, Runshan Development Zone, Jiangsu Province, P.R. China
No. 1 Zhongnan Road, Jiangyin City, Wuxi, Jiangsu Province, China
江苏科泰检测技术服务有限公司，江苏省昆山开发区金沙江南路16号，江苏省无锡江阴市申南路1号，215300
www.kttest.com

委托单位名称 Client's Unit	江西华鑫环宇科技集团有限公司		
地址/电话 Add./Tel.	江西省宜春市樟树市城北经济技术开发区清江大道 666 号		
样品描述 Sample Description	样品状态/ Sample Description: 固态/ Solid state 样品数量/ Sample Quantity: 1 样品名称/ Sample Name: 冷轧钢板 规格/ Size: 厚 1.0mm 牌号/Brand: Q235 其它/Else: /		
检测设备 Test Equipment	微机控制电液伺服万能试验机 SHT4605 Microcomputer controlled electro-hydraulic servo universal testing machine SHT4605 美国热电直读光谱仪 ARL3460 American thermoelectric direct reading spectrometer ARL3460		
检测标准 /检测项目/检测结果 Test Methods /Test Items/ Test Results	见下页 Vide infra		
送样日期 Delivering Date	2021.09.14	检验日期 Test Date	2021.09.15
检验地点 Test Place	昆山实验室 Kunshan Laboratory		
编 制 Compiled by	郝 敏		
审 核 Checked by	林 芳		
批 准 Approved by	朱 烨		



本报告是对来样负责, 并在客户提供的信息范围内。本报告在没有完整的签名、盖章情况下不允许复制。任何对结果的怀疑都应在 15 天内通知。除非另有说明, 样品只保留 30 天。This report is responsible for the receiving samples only and within the limits of information from Client. This testing report cannot be reproduced without stamp/signature of tester/checker/signatory, except in full. Any suspicion of results shown hereon should be informed within 15 days. Unless otherwise stated, samples are retained for 30 days only.

Jiangsu Science Test Service Co., Ltd. +86(0)512-36831080
 Add: No. 16 Jinshajiang South Road, Kunshan Development Zone, Jiangsu Province, P.R. China.
 No. 1, Zhongnan Road, Jiangyin City, Wuxi, Jiangsu Province, China.
 江苏科泰检测技术服务有限公司, 江苏省昆山市开发区金沙江南路 16 号, 江苏省无锡市江阴市中南路 1 号, 215300
 www.kttest.com

1. 拉伸试验/Tensile test

检测标准/Test standard: GB/T 228.1-2010

检测结果/Test result:

试样编号 Sp. No.	抗拉强度 R _m Tensile Strength (MPa)	规定塑性延伸强度 R _{p0.2} Proof Strength R _{p0.2} (MPa)	断后伸长率(A _{80mm}) Percentage Elongation after Fracture (%)	备注 Note
技术要求 Tech. req.	370~500	≥235	≥20	选自 GB/T 11253-2019, Q235 From the GB/T 11253-2019, Q235
A-1	429	333	21.5	符合 Acceptable

2. 成分分析/Component analysis

检测标准/ Test standard: GB/T 4336-2016


检测结果/Test result:

试样编号 Sp. No.	C (%)	Si (%)	Mn (%)	P (%)	S (%)	Cr (%)	Ni (%)	Cu (%)	备注 Note
技术要求 Tech. req.	≤0.22	≤0.35	≤1.40	≤0.035	≤0.035	≤0.30	≤0.30	≤0.30	选自 GB/T 11253-2019, Q235 From the GB/T 11253-2019, Q235
A-2	0.09	0.17	0.30	0.018	0.005	0.12	0.017	0.04	所测元素符合技 术要求 The measured elements meet the technical requirements

---本页结束/ End of this page---



本报告只对来样负责, 并在客户提供的信息范围内。本报告在没有完整的签名、盖章情况下不允许复制。任何对结果的怀疑都应在 15 天内通知。除非另有说明, 样品只保留 30 天。This report is responsible for the receiving samples only and within the limits of information from Client. This testing report cannot be reproduced without stamp/signature of tester/checker/signatory, except in full. Any suspicion of results shown hereon should be informed within 15 days. Unless otherwise stated, sample(s) are retained for 30 days only.
Jiangsu Science Test Service Co., Ltd., +86 (0)512-36881080
ADD: No. 16 Jinhaijiang South Road, Kunshan Development Zone, Jiangsu Province, P.R. China.
No. 1, Zhongnan Road, Jiangyin City, Wuxi, Jiangsu Province, China.
江苏科泰检测技术服务有限公司, 江苏省昆山开发区金沙江南路 16 号, 江苏省无锡江阴市中南路 1 号, 215300
---www.kttest.com---

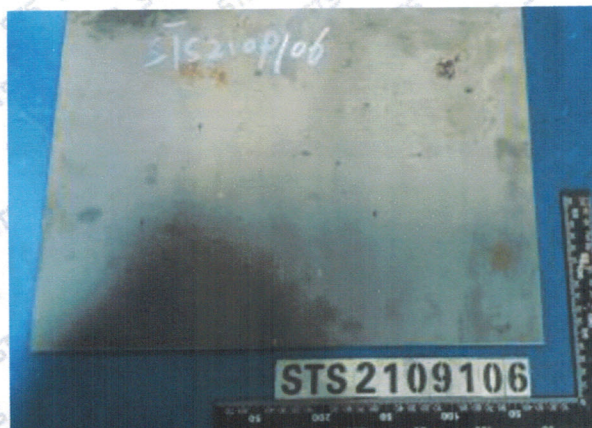

样品照片/Sample Photo

.....报告结束/End of Report.....

检测
Service
印章



本报告是对来样负责, 并在客户提供的信息范围内。本报告在没有完整的签名、盖章情况下不允许复制。任何对结果的怀疑都应在15天内通知, 除非另有说明, 样品只保留30天。This report is responsible for the receiving samples only and within the limits of information from Client. This testing report cannot be reproduced without stamp/signature of tester/checker/signatory, except in full. Any suspicion of results shown hereon should be informed within 15 days. Unless otherwise stated, sample(s) are retained for 30 days only.
Jiangsu Science Test Service Co., Ltd., +86 (0)512-36831080
ADD: No. 16 Jinchajiang South Road, Kunshan Development Zone, Jiangsu Province, P.R. China.
No. 1, Zhongnan Road, Jiangyin City, Wuxi, Jiangsu Province, China.
江苏科泰检测技术服务有限公司, 江苏省昆山开发区金沙江南路16号, 江苏省无锡市江南中南路1号, 215300
-----www.kttest.com-----